


Elmedur X

Technical Datasheet

DURO METALL

Ein Unternehmen der Wieland-Gruppe

Short Name	CW106C	Chemical	Cr	Zr	Cu
Code	CuCr1Zr	Composition	0.8	0.08	balance
Material-Nr.(old)	2.1293	(Reference values in %)			
Classification	ISO 5182 R.W.M.A.	Class A 2/2 Class 2			
Material-Properties	Precipitation hardened copper alloy with excellent hardness and high electrical and thermal conductivity.				
Applications	<ul style="list-style-type: none"> • Electrodes and cap tips for spot welding as well as for spark erosion • Contact tips for MIG/MAG welding • Parts in electrical equipments under high stress conditions if high electrical conductivity is required 				
Mechanical Properties (Reference values)	Conditions	solution annealed, cold drawn and aged		Extruded, sol. annealed and aged	Castings prec. hardened
	Cross section	<25 mm Ø	25-50 mmØ	50-120 mm Ø	-
	Hardness	HB	160	150	130
	Tensile strength	N/mm ²	min. 470	min. 440	min. 370
	Yield strength	N/mm ²	min. 440	min. 350	min. 270
	Elongation L = 5 D	%	min. 8	min. 10	min. 18
	Modulus of elasticity	kN/mm ²	108	108	108
	Modulus of torsion	kN/mm ²	45	45	45
	Squeeze strength	%	95 – 100 % of yield strength		
Physical Properties (Reference values)	Electrical conductivity 293 K (20 °C)	MS/m	43 – 50 (min.75 % I.A.C.S.) Castings 45 - 53		
	Electrical resistance 293 K (20 °C)	Ω.mm ² /m	0.021		
	Coeff. of electr. resist. 273-373 K (0-100°C)	1/K	0.00367		
	Coeff. of therm. exp. 273-593 K (0-320°C)	1/K	17,0 · 10 ⁻⁶		
	Specific heat	J/g.K	0.376		
	Thermal conductivity 293 K (20 °C)	W/m.K	c. 320		
	Density	g/cm ³	8.9		

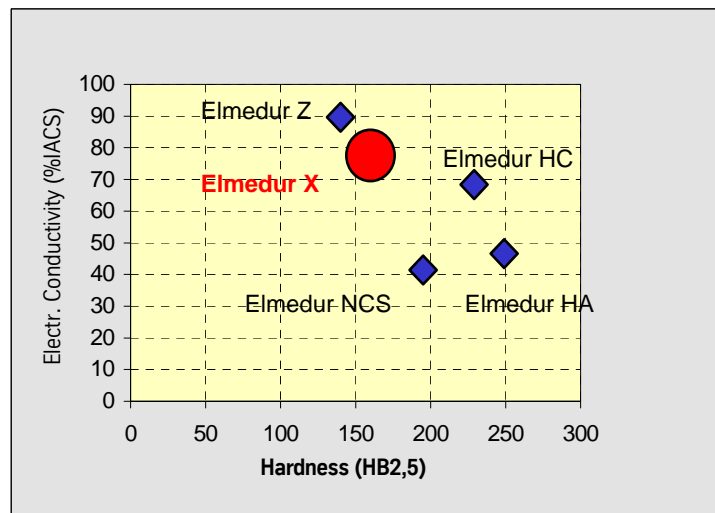


DURO METALL GmbH www.duro-metall.de

Albert-Einstein-Str. 1, D-70806 Kornwestheim, Telefon +49(0)7154 8255-0, Fax +49 (0)7154 8255-48


Elmedur X

Technical Datasheet


Electrical conductivity of Elmedur X at different temperatures

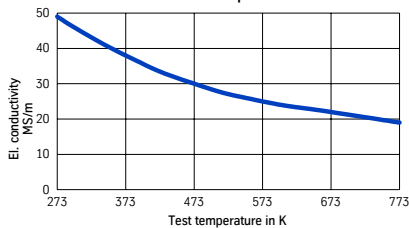

Hardness of Elmedur X at elevated temperatures

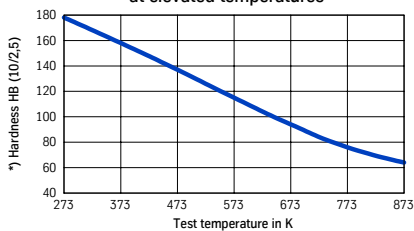

Effect of annealing temperature on hardness of Elmedur X

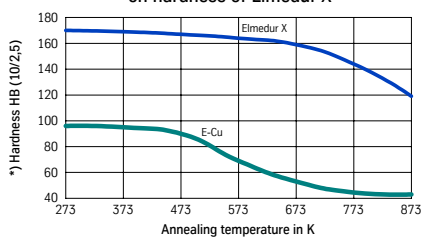

Machining (Reference values) Condition: precipitation hardened

Turning	Tungsten Carbide K 20	HSS THYRAPID 3207
Cutting speed m/min.	up to 300	up to 100
Rake angle	6 – 18	15 – 25
Feed and depth of cut	as to required surface finish	as to required surface finish
Chip breaker	recommended	recommended

Milling	Tungsten Carbide K20	HSS THYRAPID 3207
Cutting speed m/min.	up to 300	up to 100
Rake angle	positive	positive
Feed mm/min.	200 – 300	80 – 150

Drilling	Twist drills acc. to DIN 338
Cutting speed m/min.	max. 20
Chip flow	For a better chip flow, drills with an enlarged twist angle should advantageously be used. We recommend contacting the respective manufacturers.

Standards / Tolerances	
DIN EN 12 163	Round bars for general purpose
DIN EN 12 165	Ingots for forgings
DIN EN 12 167	Profiles and rectangular bars for general purpose.

Hot rolled sheets and plates

Thickness	<50 mm	-0/+2 mm
	>50 mm	-0/+3 mm
Width		+8/-0 mm

Forged sheets and flat sizes

Additions and tolerances on request

Tubes

Tolerances for tubes on request

Available sizes Bars in round, square rectangular and flat, discs and rings, forgings, electrodes for spot-, seam-, projection- and butt welding, castings on request (Available sizes can be found in our current stock list).

*) Brinell hardness at R.T. after 5-hrs heating, cooling on air

All statements as to the properties or utilization of the materials and products mentioned in this datasheet are only for the purpose of description. Guarantees in respect of the existence of certain properties or utilization at the material mentioned are only valid if agreed upon in writing.